



Acceptor and Donor Dopants in Potassium Sodium Niobate Based Ceramics

Fayaz Hussain^{1,2*}, Amir Khesro³, Zhilun Lu^{2,4}, Nouf Alotaibi⁵, Ahmad Azmin Mohamad⁶, Ge Wang², Dawei Wang² and Di Zhou^{7*}

¹ Department of Materials Engineering, NED University of Engineering & Technology, Karachi, Pakistan, ² Department of Material Science and Engineering, University of Sheffield, Sheffield, United Kingdom, ³ Department of Physics, Abdul Wali Khan University, Mardan, Pakistan, ⁴ The Henry Royce Institute, Sheffield, United Kingdom, ⁵ Chemistry Department, King Saud University, Riyadh, Saudi Arabia, ⁶ School of Materials and Mineral Resources Engineering, Universiti Sains Malaysia, Nibong Tebal, Malaysia, ⁷ Electronic Materials Research Laboratory, Key Laboratory of the Ministry of Education & International Center for Dielectric Research, Xi'an Jiaotong University, Xi'an, China

OPEN ACCESS

Edited by:

Laijun Liu,
Guilin University of Technology, China

Reviewed by:

Zhuo Li,
Chang'an University, China
Haibo Yang,
Shaanxi University of Science
and Technology, China
Yong Li,
Inner Mongolia University of Science
and Technology, China

*Correspondence:

Fayaz Hussain
fhussain@neduet.edu.pk;
engrfayazned@gmail.com
Di Zhou
zhoudi1220@xjtu.edu.cn

Specialty section:

This article was submitted to
Ceramics and Glass,
a section of the journal
Frontiers in Materials

Received: 30 March 2020

Accepted: 04 May 2020

Published: 08 July 2020

Citation:

Hussain F, Khesro A, Lu Z,
Alotaibi N, Mohamad AA, Wang G,
Wang D and Zhou D (2020) Acceptor
and Donor Dopants in Potassium
Sodium Niobate Based Ceramics.
Front. Mater. 7:160.
doi: 10.3389/fmats.2020.00160

B-site doping in potassium sodium niobate (KNN) with Mn^{2+} (Mn''_{Nb}) and Ti^{4+} (Ti'_{Nb}) dopants were soluble but prevented KNN from achieving a high relative density, while Sn^{4+} (Sn'_{Nb}) was not soluble in the structure as evidenced by second phase peaks in X-ray diffraction (XRD) traces. However, SnO_2 was an effective sintering aid in KNN-50/50. A-site doping with Sr^{2+} ($Sr_{(Na,K)}$) up to 1 mol% initially improved dielectric properties but higher sintering temperatures were required for compositions with >1 mol% Sr. Samples with 5% and 7% of Sr-doping completely shifted the transition of T_{O-T} to below RT and broadened the T_C peaks as the relaxor. All Ti-doped and Sr-doped compositions showed an increase in conductivity, manifested as high values of dielectric loss ($\tan\delta$). More than 1% of acceptor and donor dopants showed the ionic-type conduction mechanism, while 1% displayed the electronic mechanism as attributed from the strongly frequency-dependent $\tan\delta$. In conclusion, these samples have the potential to open up new applications in the field of electroceramics.



Keywords: acceptor doping, donor doping, solubility, KNN, dielectric properties

INTRODUCTION

Different properties and effects of dopants on potassium sodium niobate (KNN)-based ceramics have been discussed in many publications (Lin et al., 2007; Lee et al., 2008; Wang et al., 2008; Liu et al., 2009, 2012; Tan et al., 2012; Zhao et al., 2013; Bafandeh et al., 2014; Wu J. et al., 2014; Zheng et al., 2015; Yang et al., 2016; Hussain et al., 2019, 2020). Some groups have discussed potassium oxide and sodium oxide both separately and with doping elements, in terms of electrical properties for KNN-based ceramics (Jaffe et al., 1971; Fluckiger and Arend, 1978; Kodaira et al., 1982; Jenko et al., 2005; Lee et al., 2008; Wang et al., 2008; Zhang et al., 2013; Zhao et al., 2013; Zheng et al., 2015). Fewer studies have been done on acceptor (Akça and Yilmaz, 2015; Rafiq et al., 2015; Chen et al., 2016) and donor (Wu S. et al., 2014; Hreščak et al., 2017) dopants in KNN to understand its electrical properties. Donor and acceptor dopants play a vital role in the investigation into the semiconducting properties and defect chemistry of the well-established systems of Barium Titanate (BT) and Lead Zirconate

Titanate (PZT; Masó et al., 2006; Da-Wei et al., 2009; Cao et al., 2010; Erdem et al., 2010; Wang D. W. et al., 2011; Wang et al., 2012, 2014; Wang D. et al., 2013; Ma et al., 2012; Zhu et al., 2012; Ali et al., 2013; Freeman et al., 2013; Li et al., 2013, 2015; Lou et al., 2018). Hreščak et al. (2017) reported Sr^{2+} as a donor dopant in KNN that improved its crystal structure, grain size, and phase composition. Rafiq et al. (2015)

reported that the single acceptor-dopant of Mn^{2+} in KNN decreased the leakage current; most authors, however, have emphasized the importance of co-doping (Guo et al., 2004, 2005; Hollenstein et al., 2005; Hollenstein et al., 2007; Jiang et al., 2007; Lopez-Juarez et al., 2011; Rubio-Marcos et al., 2011; Skidmore and Milne, 2011; Wang H. Q. et al., 2011; Wang K. et al., 2013; Wang et al., 2017; Zhang et al., 2011; Li et al.,

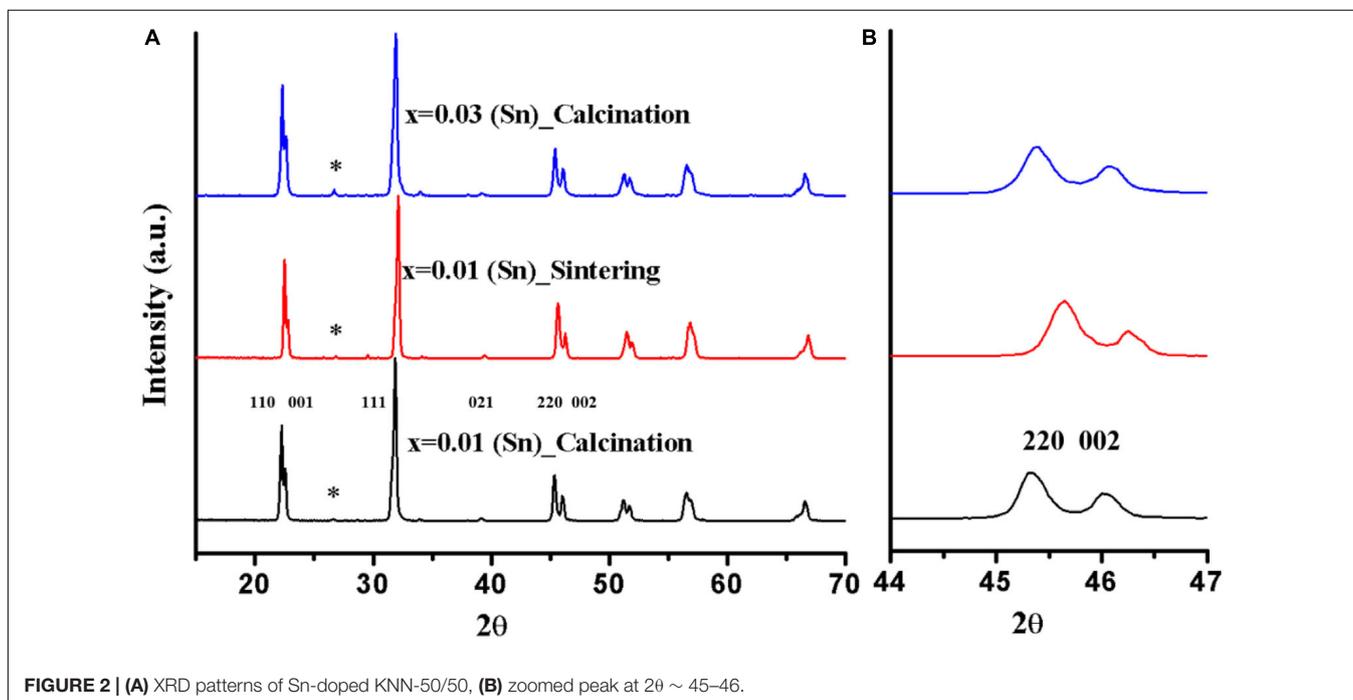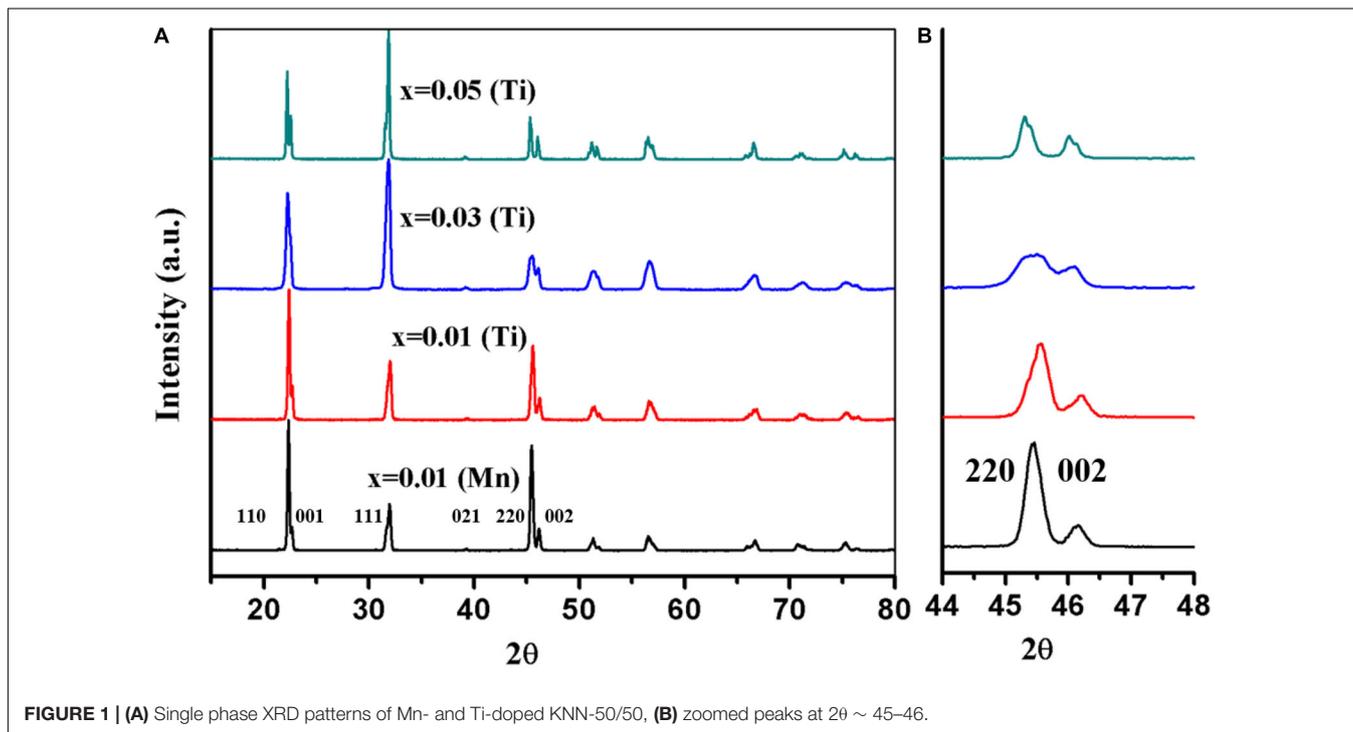

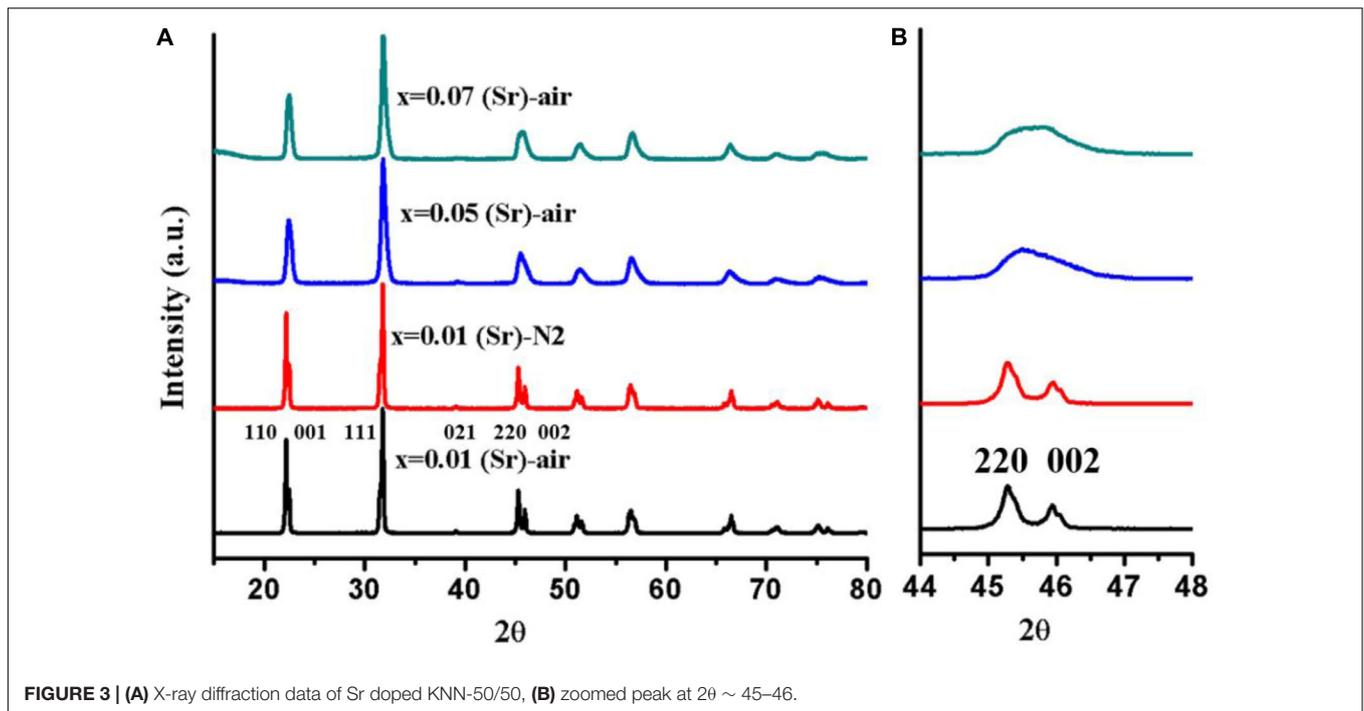


FIGURE 3 | (A) X-ray diffraction data of Sr doped KNN-50/50, (B) zoomed peak at $2\theta \sim 45\text{--}46$.

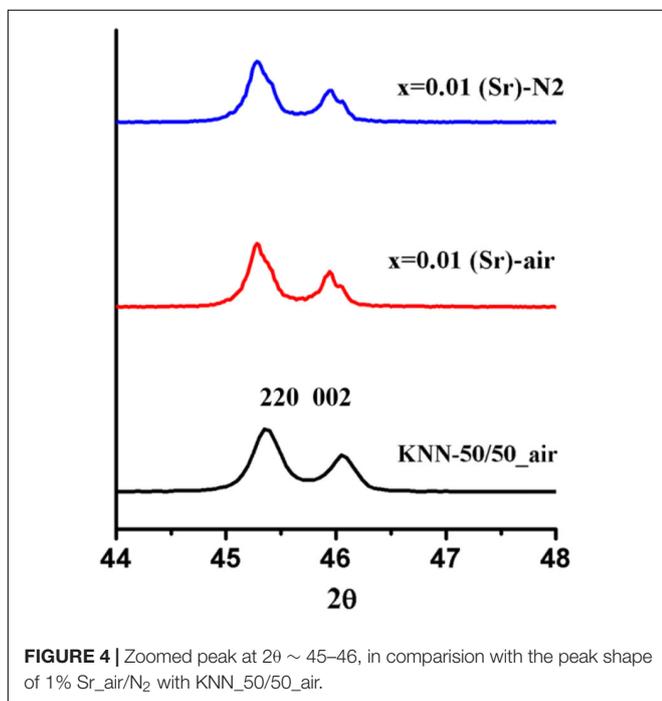



FIGURE 4 | Zoomed peak at $2\theta \sim 45\text{--}46$, in comparison with the peak shape of 1% Sr_{air}/N₂ with KNN_{50/50}-air.

2012; Du et al., 2012a,b; Gio and Phong, 2015; Liu et al., 2016, 2017) in achieving optimized functional properties. Chen et al. (2016) prepared different formulations with trace amounts of acceptor-dopants into $(K_{0.5}Na_{0.5}Nb_{0.994}A_{0.006})O_{3-\delta}$, where $A(Ga^{3+}, Ge^{4+}, Mn^{2+}, Zn^{2+}, Cu^{2+}, \text{ and } Ni^{2+})$ metallic-ions were incorporated; this consequently improved the high mechanical-quality-factor (Q_m) values in divalent-doped compositions.

The aim of this research was to introduce acceptor-dopants (Mn^{2+} , Ti^{4+} , and Sn^{4+}) and donor-dopants (Sr^{2+}) into KNN to see the individual effect of their solubility and structural changes on the electrical properties of KNN-50/50-based ceramics.

EXPERIMENTAL PROCEDURE

Nb_2O_5 was obtained from Stanford Materials Corporation with 99.999% purity, whereas K_2CO_3 and Na_2CO_3 were obtained from Fisher Scientific with 99.9% anhydrous used. In addition to this, TiO_2 was obtained from Aldrich Chemistry with 99.99%, and MnO_2 , SnO_2 , and $SrCO_3$ were obtained from Aldrich with 99.9% purity each. Carbonates were dried at $300^\circ C$, whereas all other oxides were heated at $900^\circ C$ for 24 h. Batches of 50 g of doped-KNN formulations ($K_{0.5}Na_{0.5}Ti_xNb_{1-x}O_{3-x/2}$ where $0.0 \leq x \leq 0.05$; $K_{0.5}Na_{0.5}Mn_xNb_{1-x}O_{3-x/2}$ where $0.0 \leq x \leq 0.01$; $K_{0.5}Na_{0.5}Sn_xNb_{1-x}O_{3-x/2}$ where $0.0 \leq x \leq 0.03$; and $(K_{0.5}Na_{0.5})_{1-x}Sr_xNbO_3$ where $0.0 \leq x \leq 0.07$) were prepared from dried raw powders in a hot condition ($\sim 200^\circ C$) to avoid the non-stoichiometric conditions caused by moisture, especially in carbonates. All compositions were attrition milled for 1 h in a 500 ml jar at 300 rpm in isopropanol using 3 mm Dia. Y_2O_3 stabilized zirconia milling media prior to calcination. After milling, the slurry was washed with further isopropanol, separated from milling media through a sieve, and volatiles were removed at $80^\circ C$ for 24 h in a drying oven. The dried material was sieved through a 150-micron mesh and calcined for 6 h at $850^\circ C$ at $3^\circ C/min$ and $5^\circ C/min$, heating and cooling rates, respectively. Reacted powders were re-milled before pressing a pellet. 10 mm diameter disks of all compounds were pressed uniaxially with 2-ton force and fired at in a temperature range of $1120\text{--}1165^\circ C$

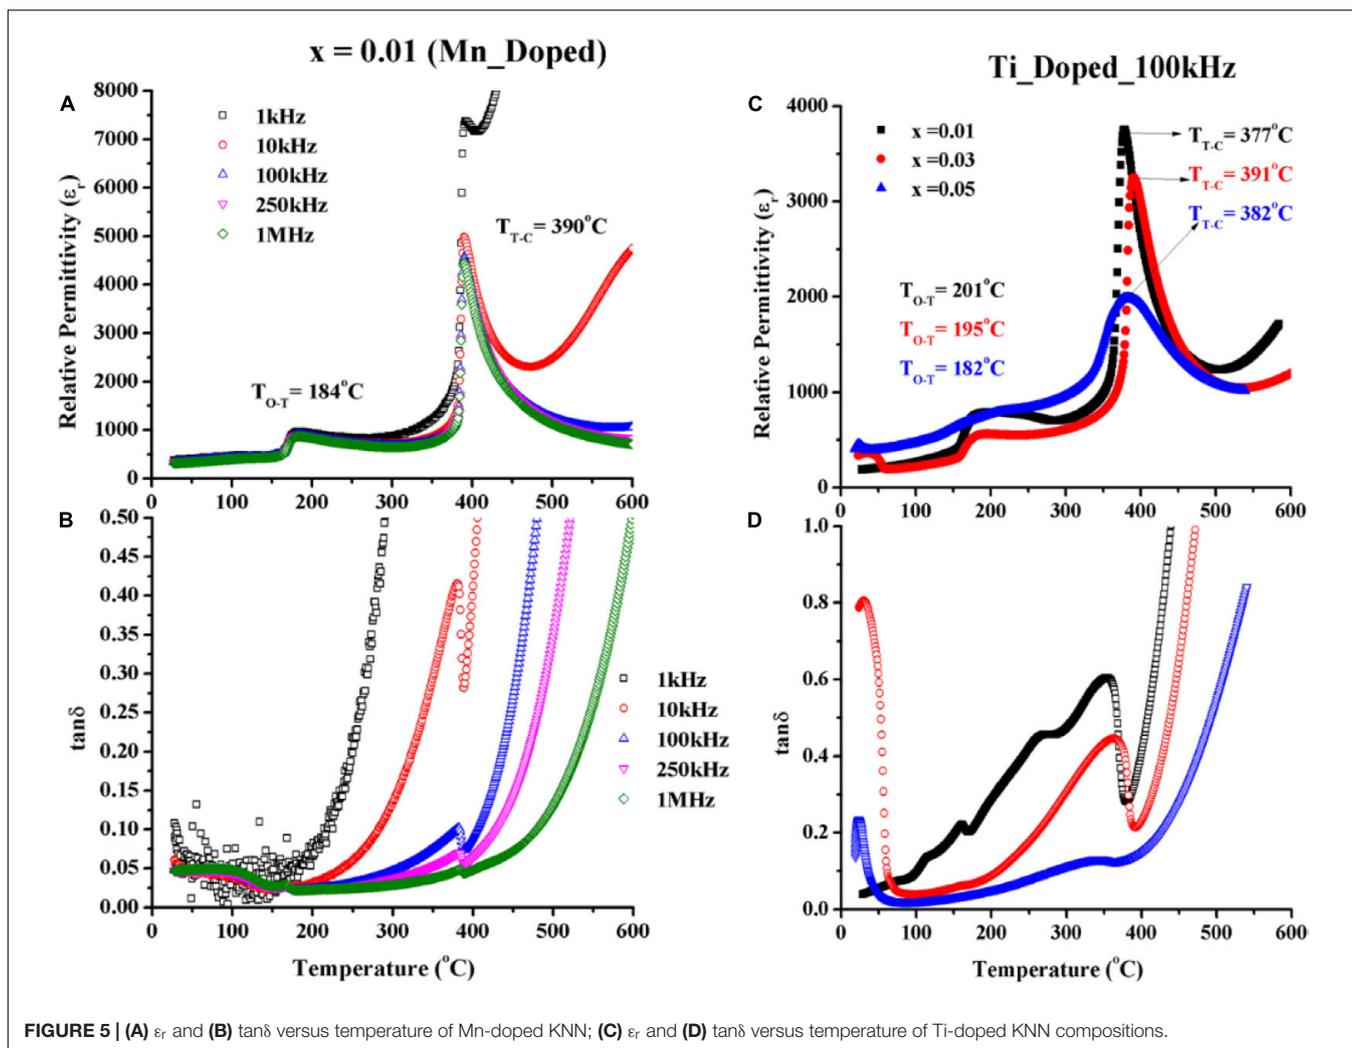

for 2–8 h. Moreover, the details of sintering temperatures of all formulations are described in **Supplementary Figures S1, S2**.

Densities of pellets were measured as per the Archimedes method, which were around 90%-bulk in average. XRD traces of sintered pellets were obtained using a Siemens D500 diffractometer at the 2θ range of 10° – 80° , using $\text{CuK}\alpha$ radiation. The dielectric properties were characterised using an LCR meter (Model 4284A, Hewlett Packard).


RESULTS AND DISCUSSION

XRD

The XRD traces from KNN-50/50 doped on the B-site with Mn^{2+} , Ti^{4+} , and Sn^{4+} are shown in **Figures 1, 2**. The XRD traces from KNN-50/50 doped with 1% Mn and 1% Ti both appear to be similar, but the shape of $2\theta \sim 45^\circ$ {220}, and {002} peaks shows a slight difference (**Figure 1**). In both cases, the intensity of the $2\theta = 32^\circ$ {111} is lower than that of the undoped KNN (Lin et al., 2010). Increasing the concentration of Ti to 5% Ti emphasized the structural change observed at 1% Ti. There

are a few studies on single Mn acceptor dopant in KNN. Peaks shifting toward higher 2θ is evidence of shrinkage in the lattice volume, which took place for Mn^{2+} (Rafiq et al., 2015) and Ti^{4+} acceptor dopants as compared to the undoped KNN peak (shown in **Figure 4**; $2\theta = 45$ – 46°). Conversely, Lin et al. (2010) reported that XRD peaks shifted toward lower 2θ (i.e., expansion in the lattice volume) in the case of Mn^{4+} doped KNN.

For KNN-50/50 doped with Sn^{4+} , secondary peaks of SnO_2 are visible in **Figure 2**. Moreover, within the resolution limits of in-house XRD, there was no discernible change in the trace of the major KNN peaks, confirming that Sn does not enter into solid solution with KNN. Su et al. (2010) investigated SnO_2 and CuO co-doping in KNN and concluded that Sn^{4+} was not soluble after 1 mol%. Their XRD traces also depicted secondary peak positions similar to those in this study. Akça and Yılmaz (2015) also reported insolubility issues for Sn^{4+} in KNN with secondary peaks visible in their XRD data. The reasons behind the insolubility of Sn^{4+} issues in KNN is unclear, since Sn^{4+} (0.69 Å) has a similar ionic radius to Nb^{5+} (0.68 Å; Shannon, 1976). However, Sn^{4+} is more covalently bonded to O than Nb^{5+} , which may influence its solubility (Barret, 1962; IBchem, 2016).

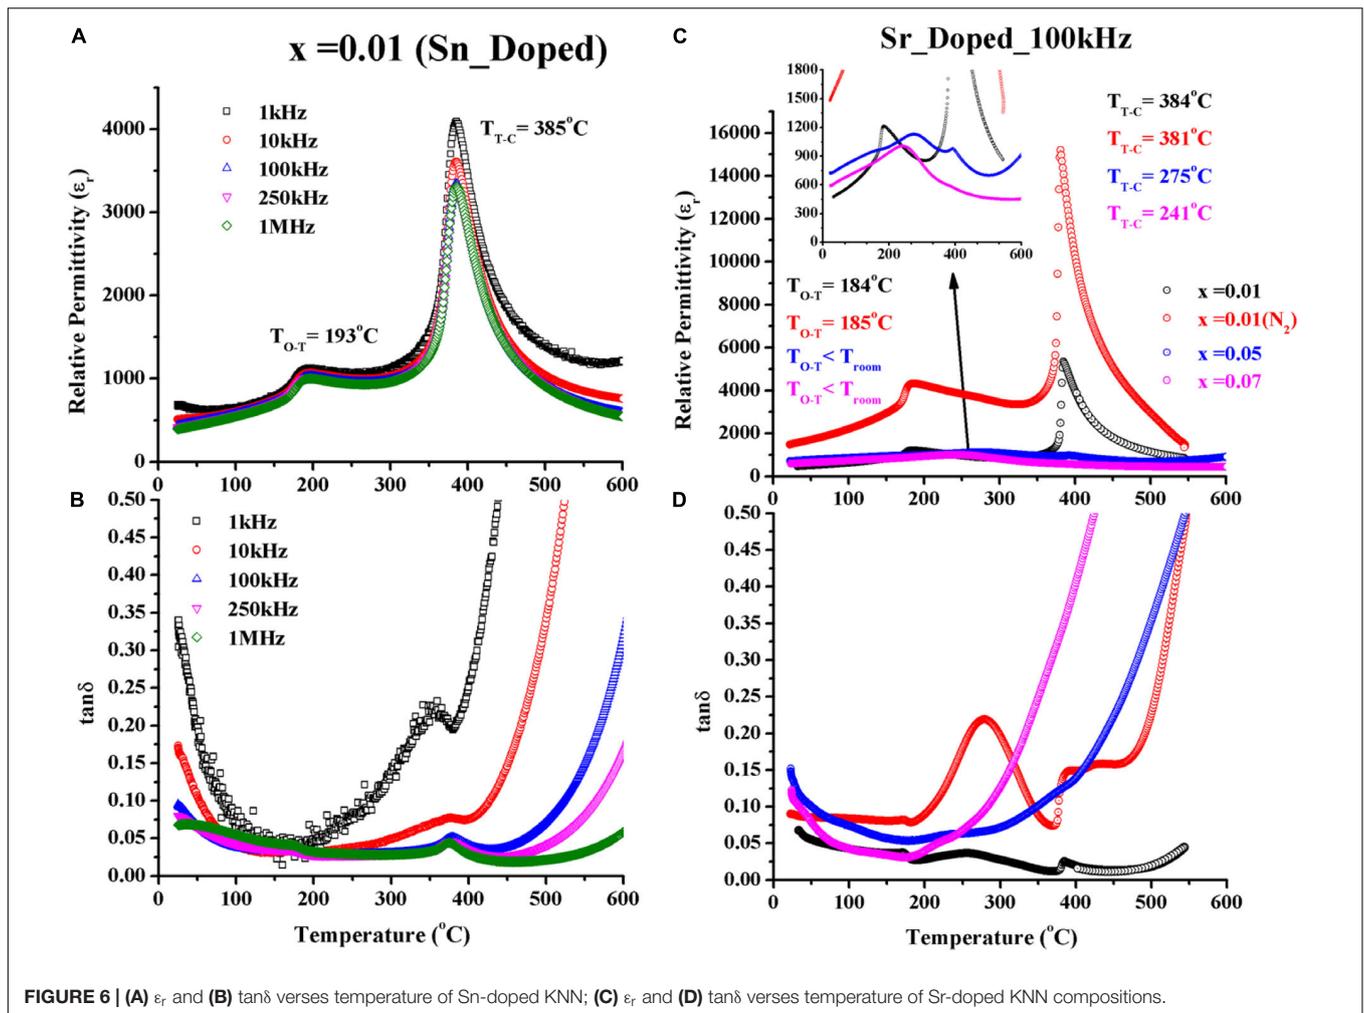


For KNN-50/50 doped with Sr^{2+} on the A-site, the XRD traces revealed a broadening of the $\{111\}$ peaks as a function of x with respect to undoped KNN-50/50 when fired in both air and N_2 . **Figures 3, 4** should be evaluated together, indicating that Sr^{2+} was incorporated within the KNN lattice.

Dielectric Properties

Acceptor Dopants: Mn^{2+} , Ti^{4+} , and Sn^{4+}

The temperature dependence of relative permittivity (ϵ_r) and loss ($\tan\delta$) of 1 mol% Mn doped KNN-50/50 are shown in **Figures 5A,B** as a function of temperature and frequency. Two phase transition temperatures, i.e., orthorhombic-tetragonal ($T_{\text{O-T}}$), and tetragonal-cubic ($T_{\text{T-C}}$) are clearly presented, though both transitions are shifted toward lower temperatures compared to undoped KNN-50/50 sintered in air. The ϵ_r and $\tan\delta$ at room temperature of 1% Mn doped KNN-50/50 was 380 and 0.05 at 100 kHz, respectively. However, at lower frequencies, the $\tan\delta$ increased dramatically when increasing the temperature. The most likely cause of $\tan\delta$ relates to oxygen vacancy ($V_{\text{O}}^{\bullet\bullet}$) formed according to the defect equation:



At high frequencies (1 MHz), $\tan\delta$ was suppressed with acceptor Mn^{2+} dopant. At these frequencies, the loss mechanism relating to $V_{\text{O}}^{\bullet\bullet}$ may clamp out, resulting in a decrease in the overall $\tan\delta$. There are a number of potential loss mechanisms relating to $V_{\text{O}}^{\bullet\bullet}$, such as rotation of defect dipoles and movement of space charge. It is not known which mechanism dominates in this study.

The dielectric properties of Ti-doped KNN-50/50 are shown in **Figures 5C,D**. For low concentrations, (1%) the $T_{\text{T-C}}$ temperature decreased with little change in $T_{\text{O-T}}$. However, for high concentrations, $T_{\text{T-C}}$ phase transition temperatures increased, and $T_{\text{O-T}}$ decreased compared to the undoped and 1% Ti doped compositions and the phase transitions become broader. The peak in permittivity at around room temperature in 3 and 5% Ti-doped KNN may relate to the observation of minor changes to the shape of some XRD peaks (at $\{220\}$ and $\{002\}$ planes; **Figure 1**). Dielectric loss in Ti-doped suppressed from $x = 0.01$ to $x = 0.05$ with respect to the temperature and frequency, which suggested that the conduction mechanism shifted from electronic to ionic as the Ti dopant increased. Nevertheless, electronic species are lighter than ionic ones; that's why ionic species need more activation energy and consequently higher conduction at higher temperatures (see **Supplementary Data**).

The dielectric properties of Sn^{4+} doped KNN are shown in **Figures 6A,B**. Unsurprisingly, there was no effect on the dielectric properties with respect to undoped compositions since there was no evidence that Sn^{4+} enters the KNN lattice.

Donor Dopant: Sr^{2+}

Dielectric properties of Sr donor dopant (A-site) in KNN-50/50 are presented in **Figures 6C,D**. 1% Sr-doped KNN-50/50 compositions were sintered in both air and N_2 to compare the behavior with undoped in a previous study (Hussain et al., 2018) and acceptor doped compositions in the previous sections. However, for undoped KNN sintered in N_2 , the transition temperature decreased in agreement with 1% Sr-doped KNN (N_2). N_2 sintered Sr^{2+} KNN becomes more conductive as compared to undoped KNN, presumably because Sr^{2+} donates extra electrons (h^\cdot) and low $p\text{O}_2$ creates $V_{\text{O}}^{\cdot\cdot}$. It has been proposed that the increase in conductivity contributes to the larger permittivity for N_2 sintered KNN-1 Sr. $T_{\text{T-C}}$ with acceptor (Mn^{2+}) and donor (Sr^{2+}) in air are 390°C and 384°C , respectively, which suggests that disruption of the ferroelectric order to reduce $T_{\text{T-C}}$ is greater for A-site Sr^{2+} doping in comparison to B-site Mn^{2+} . At higher Sr concentrations, $x = 0.05$ and 0.07 , the phase transitions broaden in temperature (inset of **Figure 6C**), consistent with the broadening of peaks in the XRD traces (**Figure 3**). In addition, the dielectric loss increased when samples became more conductive at higher than 1% Sr (see **Supplementary Data**). Nonetheless, this broadening and higher dielectric loss phenomenon with donor doping looks similar to the results reported in the case of W^{6+} B-site donor doping in KNN, investigated by Wu S. et al. (2014).

CONCLUSION

Acceptor dopants such as Mn^{2+} (Mn_{Nb}''') and Ti^{4+} (Ti_{Nb}'') at the B-site of KNN were incorporated to modify properties, but they both inhibited densification of KNN. Nonetheless, both acceptor species were soluble in the lattice, as revealed by XRD. Dielectric losses increased dramatically at lower frequencies with increasing temperatures by using acceptors but were moderately lower at higher frequencies. A further B-site dopant (Sn^{4+}) was also attempted but was insoluble, as evidenced by the appearance of secondary phase peaks in XRD data at low concentrations. Nevertheless, Sn^{4+} was an effective sintering aid in KNN-50/50

REFERENCES

- Akça, E., and Yilmaz, H. (2015). Sintering behavior and electrical properties of $\text{K}_4\text{CuNb}_8\text{O}_{23}$ modified $\text{K}_0.5\text{Na}_0.5\text{NbO}_3$ ceramics with SnO_2 , ZnO or Yb_2O_3 doping. *Ceramics Int.* 41, 3659–3667. doi: 10.1016/j.ceramint.2014.11.035
- Ali, A. I., Ahn, C. W., and Kim, Y. S. (2013). Enhancement of piezoelectric and ferroelectric properties of BaTiO_3 ceramics by aluminum doping. *Ceramics Int.* 39, 6623–6629. doi: 10.1016/j.ceramint.2013.01.099
- Bafandeh, M. R., Gharakhani, R., Abbasi, M. H., Saidi, A., Lee, J.-S., and Han, H.-S. (2014). Improvement of piezoelectric and ferroelectric properties in $(\text{K},\text{Na})\text{NbO}_3$ -based ceramics via microwave sintering. *J. Electr.* 33, 128–133. doi: 10.1007/s10832-014-9951-z

and improved its relative density. Ceramic density improved with 1 mol% Sr^{2+} but at a higher sintering temperature. Sr^{2+} -doped formulations showed higher conductivity, which manifested itself in higher values of $\tan\delta$. T_{C} of KNN-1 Sr in N_2 decreased with respect to air-sintered samples.

DATA AVAILABILITY STATEMENT

The raw data supporting the conclusions of this article will be made available by the authors, without undue reservation.

AUTHOR CONTRIBUTIONS

FH: Investigation, software, data analysis, original draft writing, and critical discussion of results, etc. AK: Formal discussion, review and editing, and language. ZL: Conceptualization, review, and editing. NA, GW, and DZ: Review, editing, and technical additions. AM: Review, editing, and technical discussion. DW: Review, editing, formal analysis, and critical discussion. All authors contributed to the article and approved the submitted version.

FUNDING

FH acknowledges NED University of Engineering and Technology, Pakistan, for funding support. All authors acknowledge financial help from the Sustainability and Substitution of Functional Materials and Devices EPSRC grant (EP/L017563/1) through Prof. Ian M. Reaney. The data of this work is from Ph.D. thesis of FH (Corresponding Author; Hussain, 2016). ZL acknowledges the Henry Royce Institute for Advanced Materials, funded through EPSRC grants EP/R00661X/1, EP/S019367/1, EP/P02470X/1, and EP/P025285/1.

SUPPLEMENTARY MATERIAL

The Supplementary Material for this article can be found online at: <https://www.frontiersin.org/articles/10.3389/fmats.2020.00160/full#supplementary-material>

- Barret, R. L. (1962). Electronegativity Chart. *J. Chem. Educ.* 39:251. doi: 10.1021/ed039p251
- Cao, M.-S., Wang, D.-W., Yuan, J., Lin, H.-B., Zhao, Q.-L., Song, W.-L., et al. (2010). Enhanced piezoelectric and mechanical properties of ZnO whiskers and Sb_2O_3 co-modified lead zirconate titanate composites. *Mater. Lett.* 64, 1798–1801. doi: 10.1016/j.matlet.2010.05.037
- Chen, K., Zhang, F., Li, D., Tang, J., Jiao, Y., and An, L. (2016). Acceptor doping effects in $(\text{K}_0.5\text{Na}_0.5)\text{NbO}_3$ lead-free piezoelectric ceramics. *Ceramics Int.* 42, 2899–2903. doi: 10.1016/j.ceramint.2015.11.016
- Da-Wei, W., De-Qing, Z., Jie, Y., Quan-Liang, Z., Hong-Mei, L., Zhi-Ying, W., et al. (2009). Structural and electrical properties of Nd ion modified lead zirconate titanate nanopowders and ceramics. *Chin. Phys. B* 18:2596. doi: 10.1088/1674-1056/18/6/079

- Du, J., Yi, X.-J., Ban, C.-L., Xu, Z.-J., Zhao, P.-P., and Wang, C.-M. (2012a). Piezoelectric properties and time stability of lead-free $(\text{Na}_0.52\text{K}_0.44\text{Li}_0.04)\text{Nb}_{1-x}\text{ySb}_x\text{Ta}_y\text{O}_3$ ceramics. *Ceramics Int.* 39, 2135–2139. doi: 10.1016/j.ceramint.2012.07.063
- Du, J., Yi, X.-J., Xu, Z.-J., Ban, C.-L., Zhang, D.-F., Zhao, P.-P., et al. (2012b). Effects of CaAl_2O_4 on the electrical properties and temperature stability of $(\text{Na}_0.53\text{K}_0.40\text{Li}_0.066)\text{Nb}_0.92\text{Sb}_0.08\text{O}_3$ ceramics. *J. Alloys Compounds* 541, 454–457. doi: 10.1016/j.jallcom.2012.07.039
- Erdem, E., Eichel, R. A., and Fetzer, C., Dézsi, I., Lauterbach, S., Kleebe, H. J., et al. (2010). Site of incorporation and solubility for Fe ions in acceptor-doped PZT ceramics. *Journal of Applied Physics* 107, 054109. doi: 10.1063/1.3327436
- Hussain, F. (2016). *Lead-Free KNN-based Piezoelectric Ceramics*. PhD thesis, The University of Sheffield, United Kingdom.
- Fluckiger, U. and Arend, H. (1978). On the preparation of pure, doped and reduced KNbO_3 single crystals. *J. Crystal Growth* 43, 406–416. doi: 10.1016/0022-0248(78)90338-x
- Freeman, C. L., Dawson, J. A., Chen, H.-R., Ben, L., Harding, J. H., Morrison, F. D., et al. (2013). Energetics of Donor-Doping, Metal Vacancies, and Oxygen-Loss in A-Site Rare-Earth-Doped BaTiO_3 . *Adv. Funct. Mater.* 23, 3925–3928. doi: 10.1002/adfm.201203147
- Gio, P. D., and Phong, N. D. (2015). Effects of LiF on the Structure and Electrical Properties of $(\text{Na}_{0.52}\text{K}_{0.435}\text{Li}_{0.045})\text{Nb}_{0.87}\text{Sb}_{0.08}\text{Ta}_{0.05}\text{O}_3$ Lead-Free Piezoelectric Ceramics Sintered at Low Temperatures. *J. Mater. Sci. Chem. Eng.* 03, 13–20. doi: 10.4236/msce.2015.311003
- Guo, Y., Kakimoto, K. I., and Ohsato, H. (2004). Phase transitional behavior and piezoelectric properties of $(\text{Na}_{\text{sub}0.5}\text{K}_{\text{sub}0.5})\text{NbO}_{\text{sub}3}\text{-LiNbO}_{\text{sub}3}$ ceramics. *Appl. Phys. Lett.* 85:4121.
- Guo, Y., Kakimoto, K. I., and Ohsato, H. (2005). $(\text{Na}_0.5\text{K}_0.5)\text{NbO}_3\text{-LiTaO}_3$ lead-free piezoelectric ceramics. *Mater. Lett.* 59, 241–244. doi: 10.1016/j.matlet.2004.07.057
- Hollenstein, E., Damjanovic, D., and Setter, N. (2007). Temperature stability of the piezoelectric properties of Li-modified KNN ceramics. *J. Eur. Ceramic Soc.* 27, 4093–4097. doi: 10.1016/j.jeurceramsoc.2007.02.100
- Hollenstein, E., Davis, M., Damjanovic, D., and Setter, N. (2005). Piezoelectric properties of Li- and Ta-modified $(\text{K}_{\text{sub}0.5}\text{Na}_{\text{sub}0.5})\text{NbO}_{\text{sub}3}$ ceramics. *Appl. Phys. Lett.* 87:182905.
- Hreščak, J., Dražić, G., Deluca, M., Arèon, I., Kodre, A., Dapiaggi, M., et al. (2017). Donor doping of $\text{K}_0.5\text{Na}_0.5\text{NbO}_3$ ceramics with strontium and its implications to grain size, phase composition and crystal structure. *J. Eur. Ceramic Soc.* 37, 2073–2082. doi: 10.1016/j.jeurceramsoc.2016.12.053
- Hussain, F., Sterianou, I., Khesro, A., Sinclair, D. C., and Reaney, I. (2018). p-Type/n-type behaviour and functional properties of $\text{K}_x\text{Na}_{(1-x)}\text{NbO}_3$ ($0.49 \leq x \leq 0.51$) sintered in air and N_2 . *J. Eur. Ceramic Soc.* 38, 3118–3126. doi: 10.1016/j.jeurceramsoc.2018.03.013
- Hussain, F., Khesro, A., Lu, Z., Wang, G., and Wang, D. (2020). Lead free multilayer piezoelectric actuators by economically new approach. *Front. Mater.* 7:87. doi: 10.3389/fmats.2020.00087
- Hussain, F., Khesro, A., Muhammad, R., and Wang, D. (2019). Effect of Ta-doping on functional properties of $\text{K}_0.51\text{Na}_0.49\text{NbO}_3$. *Mater. Res. Expr.* 6:106309. doi: 10.1088/2053-1591/ab3d49
- IBChem (2016). *Covalent Bond*. Brussels: IBChem.
- Jaffe, B., Cook, W. R. J., and Jaffe, H. (1971). *Piezoelectric Ceramics*. New York, NY: Academic Press.
- Jenko, D., Bencan, A., Malic, B., Holc, J., and Kosce, M. (2005). Electron microscopy studies of potassium sodium niobate ceramics. *Microsc Microanal* 11, 572–580. doi: 10.1017/s1431927605050683
- Jiang, X. P., Hu, X. P., Jiang, F. L., Liu, X. D., and Yin, Q. R. (2007). Li-modified sodium potassium tantalum niobate lead-free piezoelectric ceramics. *J. Inorgan. Mater.* 22, 465–468.
- Kodaira, K., Shioya, J., Shimada, S., Matsushita, T. (1982). Sintering and dielectric properties of KNbO_3 . *J. Mater. Sci. Lett.* 1, 277–278.
- Lee, Y.-H., Cho, J.-H., Kim, B.-I., and Choi, D.-K. (2008). Piezoelectric Properties and Densification Based on Control of Volatile Mass of Potassium and Sodium in $(\text{K}_0.5\text{Na}_0.5)\text{NbO}_3$ Ceramics. *Jpn. J. Appl. Phys.* 47, 4620–4622. doi: 10.1143/jjap.47.4620
- Li, Y., Dai, Y.-J., Wang, H.-Q., Sun, T., Xu, W., and Zhang, X.-W. (2012). Microstructures and electrical properties of KNbO_3 doped (Li,Ta,Sb) modified $(\text{K,Na})\text{NbO}_3$ lead-free ceramics by two-step sintering. *Mater. Lett.* 89, 70–73. doi: 10.1016/j.matlet.2012.08.061
- Li, Y., Wang, D., Cao, W., Li, B., Yuan, J., Zhang, D., et al. (2015). Effect of MnO_2 addition on relaxor behavior and electrical properties of PMNST ferroelectric ceramics. *Ceramics Int.* 41, 9647–9654. doi: 10.1016/j.ceramint.2015.04.030
- Li, Y., Yuan, J., Wang, D., Zhang, D., Jin, H., and Cao, M. (2013). Effects of Nb, Mn doping on the structure, piezoelectric, and dielectric Properties of $0.8\text{Pb}(\text{Sn}_{0.46}\text{Ti}_{0.54})\text{O}_3\text{-}0.2\text{Pb}(\text{Mg}_{1/3}\text{Nb}_{2/3})\text{O}_3$ piezoelectric ceramics. *J. Am. Ceramic Soc.* 96, 3440–3447.
- Lin, D., Li, Z., Zhang, S., Xu, Z., Yao, X. (2010). Influence of MnO_2 doping on the dielectric and piezoelectric properties and domain structure in $(\text{K}_{0.5}\text{Na}_{0.5})\text{NbO}_3$ single crystals. *J. Am. Ceramic Soc.* 93, 941–944.
- Lin, D., Kwok, K. W., and Chan, H. W. L. (2007). Dielectric and piezoelectric properties of $(\text{K}_{0.50}\text{Na}_{0.50}\text{NbO}_3\text{-BaZr}_{0.050}\text{Ti}_{0.950}\text{O}_3)$ lead-free ceramics. *Appl. Phys. Lett.* 91:143513.
- Liu, L., Fan, H., Fang, L., Chen, X., Dammak, H., and Thi, M. P. (2009). Effects of Na/K evaporation on electrical properties and intrinsic defects in $\text{Na}_0.5\text{K}_0.5\text{NbO}_3$ ceramics. *Mater. Chem. Phys.* 117, 138–141. doi: 10.1016/j.matchemphys.2009.05.024
- Liu, L., Huang, Y., Li, Y., Fang, L., Dammak, H., Fan, H., et al. (2012). Orthorhombic to tetragonal structural phase transition in $\text{Na}_0.5\text{K}_0.5\text{NbO}_3$ -based ceramics. *Mater. Lett.* 68, 300–302. doi: 10.1016/j.matlet.2011.10.103
- Liu, L., Knapp, M., Ehrenberg, H., Fang, L., Fan, H., Schmitt, L. A., et al. (2017). Average vs. local structure and composition-property phase diagram of $\text{K}_0.5\text{Na}_0.5\text{NbO}_3\text{-Bi}^{1/2}\text{Na}^{1/2}\text{TiO}_3$ system. *J. Eur. Ceramic Soc.* 37, 1387–1399. doi: 10.1016/j.jeurceramsoc.2016.11.024
- Liu, L., Knapp, M., Ehrenberg, H., Fang, L., Schmitt, L. A., Fuess, H., et al. (2016). The phase diagram of $\text{K}_0.5\text{Na}_0.5\text{NbO}_3\text{-Bi}^{1/2}\text{Na}^{1/2}\text{TiO}_3$. *J. Appl. Crystallogr.* 49, 574–584. doi: 10.1107/s16005767160002909
- Lopez-Juarez, R., Gonzalez-Garcia, F., Zarate-Medina, J., Escalona-Gonzalez, R., and de la Torre, S. D., and Villafuerte-Castrejon, M. E. (2011). Piezoelectric properties of Li-Ta co-doped potassium-sodium niobate ceramics prepared by spark plasma and conventional sintering. *J. Alloys Compounds* 509, 3837–3842. doi: 10.1016/j.jallcom.2010.12.103
- Lou, Q., Shi, X., Ruan, X., Zeng, J., Man, Z., Zheng, L., et al. (2018). Ferroelectric properties of Li-doped BaTiO_3 ceramics. *J. Am. Ceramic Soc.* 101, 3597–3604.
- Ma, N., Zhang, B.-P., and Yang, W.-G. (2012). Low-temperature sintering of Li_2O -doped BaTiO_3 lead-free piezoelectric ceramics. *J. Electroceram.* 28, 275–280. doi: 10.1007/s10832-012-9730-7
- Masó, N., Beltrán, H., Cordoncillo, E., Flores, A. A., Escribano, P., Sinclair, D. C., et al. (2006). Synthesis and electrical properties of Nb-doped BaTiO_3 . *J. Mater. Chem.* 16, 3114–3119. doi: 10.1039/b601251e
- Rafiq, M. A., Tkach, A., Costa, M. E., Vilarinho, P. M. (2015). Defects and charge transport in Mn-doped $\text{K}_{0.5}\text{Na}_{0.5}\text{NbO}_3$ ceramics. *Phys. Chem. Chem. Phys.* 17, 24403–24411. doi: 10.1039/c5cp02883c
- Rubio-Marcos, F., Romero, J. J., Fernández, J. F., and Marchet, P. (2011). Control of the Crystalline Structure and Piezoelectric Properties of $(\text{K,Na,Li})(\text{Nb,Ta,Sb})\text{O}_3$ Ceramics through Transition Metal Oxide Doping. *Appl. Phys. Expr.* 4:101501. doi: 10.1143/apex.4.101501
- Shannon, R. D. (1976). Revised effective ionic radii and systematic studies of interatomic distances in halides and chalcogenides. *Acta Crystallogr. Sec. A* 32, 751–767. doi: 10.1107/s0567739476001551
- Skidmore, T. A., and Milne, S. J. (2011). Phase development during mixed-oxide processing of a $[\text{Na}_{0.5}\text{K}_{0.5}\text{NbO}_3]_{1-x}\text{-}[\text{LiTaO}_3]_x$ powder. *J. Mater. Res.* 22, 2265–2272. doi: 10.1557/jmr.2007.0281
- Su, S., Zuo, R., Wang, X., and Li, L. (2010). Sintering, microstructure and piezoelectric properties of CuO and SnO_2 co-modified sodium potassium niobate ceramics. *Mater. Res. Bull.* 45, 124–128. doi: 10.1016/j.materresbull.2009.09.033
- Tan, C. K. I., Yao, K., Goh, P. C., and Ma, J. (2012). $0.94(\text{K}_0.5\text{Na}_0.5)\text{NbO}_3\text{-}0.06\text{LiNbO}_3$ piezoelectric ceramics prepared from the solid state reaction modified with polyvinylpyrrolidone (PVP) of different molecular weights. *Ceramics Int.* 38, 2513–2519. doi: 10.1016/j.ceramint.2011.11.021
- Wang, D., Hussain, F., Khesro, A., Feteira, A., Tian, Y., Zhao, Q., et al. (2017). Composition and temperature dependence of structure and piezoelectricity

- in (1-x)(K_{1-y}Na_y)NbO_{3-x}(Bi^{1/2}Na^{1/2})ZrO₃ lead-free ceramics. *J. Am. Ceramic Soc.* 100, 627–637. doi: 10.1111/jace.14589
- Wang, D., Li, J., Cao, M., and Zhang, S. (2014). Effects of Nb₂O₅ additive on the piezoelectric and dielectric properties of PHT-PMN ternary ceramics near the morphotropic phase boundary. *Phys. Status Solidi. A Appl. Mater. Sci.* 211, 226–230. doi: 10.1002/pssa.201330203
- Wang, D., Zhao, Q., Cao, M., Cui, Y., and Zhang, S. (2013). Dielectric, piezoelectric, and ferroelectric properties of Al₂O₃ and MnO₂ modified Pb_{0.3}Sn_{0.3}PbTiO₃ (Mg^{1/3}Nb^{2/3})O₃ ternary ceramics. *Phys. Status Solidi* 210, 1363–1368. doi: 10.1002/pssa.201228760
- Wang, D. W., Cao, M. S., Yuan, J., Zhao, Q. L., Li, H. B., Zhang, D. Q., et al. (2011). Enhanced Piezoelectric and Ferroelectric Properties of Nb₂O₅ Modified Lead Zirconate Titanate-Based Composites. *J. Am. Ceramic Soc.* 94, 647–650. doi: 10.1111/j.1551-2916.2010.04309.x
- Wang, D.-W., Yuan, J., Li, H.-B., Lu, R., Zhao, Q.-L., Zhang, D.-Q., et al. (2012). Effects of Nb₂O₅ addition on the microstructure, electrical, and mechanical properties of PZT/ZnO nanowisker piezoelectric composites. *J. Mater. Sci.* 47, 2687–2694. doi: 10.1007/s10853-011-6094-3
- Wang, H. Q., Zuo, R. Z., Fu, J. A., and Liu, Y. (2011). Sol-gel derived (Li, Ta, Sb) modified sodium potassium niobate ceramics: processing and piezoelectric properties. *J. Alloys Compounds* 509, 936–941. doi: 10.1016/j.jallcom.2010.09.134
- Wang, K., Yao, F.-Z., Jo, W., Gobeljic, D., Shvartsman, V. V., Lupascu, D. C., et al. (2013). Temperature-Insensitive (K,Na)NbO₃-Based Lead-Free Piezoactuator Ceramics. *Adv. Funct. Mater.* 23, 4079–4086. doi: 10.1002/adfm.201203754
- Wang, Y., Damjanovic, D., Klein, N., and Setter, N. (2008). High-Temperature Instability of Li- and Ta-Modified (K,Na)NbO₃ Piezoceramics. *J. Am. Ceramic Soc.* 91, 1962–1970. doi: 10.1111/j.1551-2916.2008.02392.x
- Wu, J., Wang, X., Cheng, X., Zheng, T., Zhang, B., Xiao, D., et al. (2014). New potassium-sodium niobate lead-free piezoceramic: Giant-d₃₃ vs. sintering temperature. *J. Appl. Phys.* 115:114104. doi: 10.1063/1.4868585
- Wu, S., Zhu, W., Liu, L., Shi, D., Zheng, S., Huang, Y., et al. (2014). Dielectric properties and defect chemistry of WO₃-doped K_{0.5}Na_{0.5}NbO₃ ceramics. *J. Electr. Mater.* 43, 1055–1061.
- Yang, X., Cheng, Z., Cheng, J., Wang, D., Shi, F., Zheng, G., et al. (2016). Structural and ferroelectric properties of textured KNN thick films prepared by sol-gel methods. *Integr. Ferroelectr.* 176, 171–178. doi: 10.1080/10584587.2016.1252242
- Zhang, D.-Q., Wang, D.-W., Zhu, H.-B., Yang, X.-Y., Lu, R., Wen, B., et al. (2013). Synthesis and characterization of single-crystalline (K, Na)NbO₃ nanorods. *Ceramics Int.* 39, 5931–5935. doi: 10.1016/j.ceramint.2012.11.065
- Zhang, L., Shen, J., Yu, J., Zhao, H., Xiu, Z., Yan, C., et al. (2011). Normal sintering and electric properties of (K,Na,Li)(Nb,Sb)O₃ lead-free piezoelectric ceramics. *J. Electroceram.* 26, 105–111. doi: 10.1007/s10832-011-9636-9
- Zhao, Y., Huang, R., Liu, R., Zhou, H., and Zhao, W. (2013). Low-temperature sintering of KNN with excess alkaline elements and the study of its ferroelectric domain structure. *Curr. Appl. Phys.* 13, 2082–2086. doi: 10.1016/j.cap.2013.08.015
- Zheng, T., Wu, J., Xiao, D., and Zhu, J. (2015). Giant d₃₃ in nonstoichiometric (K,Na)NbO₃-based lead-free ceramics. *Script. Mater.* 94, 25–27. doi: 10.1016/j.scriptamat.2014.09.008
- Zhu, W., Fujii, I., Ren, W., Trolier-McKinstry, S., and Jones, J. (2012). Domain Wall Motion in A and B Site Donor-Doped Pb(Zr_{0.52}Ti_{0.48})O₃ Films. *J. Am. Ceramic Soc.* 95, 2906–2913. doi: 10.1111/j.1551-2916.2012.05243.x

Conflict of Interest: The authors declare that the research was conducted in the absence of any commercial or financial relationships that could be construed as a potential conflict of interest.

Copyright © 2020 Hussain, Khesro, Lu, Alotaibi, Mohamad, Wang, Wang and Zhou. This is an open-access article distributed under the terms of the Creative Commons Attribution License (CC BY). The use, distribution or reproduction in other forums is permitted, provided the original author(s) and the copyright owner(s) are credited and that the original publication in this journal is cited, in accordance with accepted academic practice. No use, distribution or reproduction is permitted which does not comply with these terms.